

Polycrystalline Thin Film Device Degradation Studies

D.S. Albin, T.J. McMahon, J.W. Pankow, and
R. Noufi
National Renewable Energy Laboratory

S.H. Demtsu and A. Davies
Colorado State University

*Presented at the 2005 DOE Solar Energy Technologies
Program Review Meeting
November 7–10, 2005
Denver, Colorado*

Conference Paper
NREL/CP-520-39003
November 2005

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>



Polycrystalline Thin Film Device Degradation Studies

D.S. Albin,¹ S.H. Demtsu,² T.J. McMahon,¹ A. Davies,² J.W. Pankow,¹ and R. Noufi¹
¹National Renewable Energy Laboratory, Golden, Colorado, david_albin@nrel.gov
²Colorado State University, Fort Collins, Colorado

ABSTRACT

Oxygen during vapor CdCl₂ (VCC) treatments significantly reduced resistive shunts observed in CdS/CdTe polycrystalline devices using thinner CdS layers during 100 °C, open-circuit, 1-sun accelerated stress testing. Cu oxidation resulting from the reduction of various trace oxides present in as-grown and VCC treated films is the proposed mechanism by which Cu diffusion, and subsequent shunts are controlled. Graphite paste layers between metallization and CdTe behave like diffusion barriers and similarly benefit device stability. Ni-based contacts form a protective Ni₂Te₃ intermetallic layer that reduces metal diffusion but degrades performance through increased series resistance.

1. Objectives

The objective of this work is to identify and provide solutions for device-level stability issues that can negatively impact polycrystalline thin film module reliability goals for 20-30 year lifetimes as specified in the DOE-EERE Solar Program Multi-Year Technical Plan for 2003-2007 and beyond.

2. Technical Approach

The scope of this project involves the maintenance and use of a reproducible close-spaced sublimation (CSS) based CdTe fabrication process linked with downstream performance and stability metrics through a relational database. Experiments typically involve varying key parameters associated with *how* devices are made, and subsequently studying the *impact* of these changes on performance and stability. For some experiments, software is used to design efficient, large sample size sets that yield linear regression stability models. These models are used to identify significant primary effects that have the greatest impact on stability. Smaller experiments, with an emphasis on device characterization, are then used to develop the *fundamental science* explaining these empirical observations.

3. Results and Accomplishments

Two separate studies are discussed in this paper. In the first study, a large orthogonal experiment (48 devices) was used to determine how stability was affected when the CdS and CdTe film thickness was varied between 60 to 100 nm and 8 to 11 microns respectively. This study also involved determining the effects of nitric-phosphoric (NP) acid as a pre-contact etch and oxygen as an additive to the VCC process. In

the second study, the use of graphite layers with Ag and Ni-based adhesive backcontact pastes was investigated. In both studies, stability was ascertained by making current density-voltage (JV) measurements periodically after stressing devices under 1-sun, open-circuit bias at 100°C.

3.1 Film Thickness and VCC Oxygen Effects

Linear regression models correlating performance and stability with film thickness, the use of NP etch, and the presence of oxygen during the VCC process were developed using JMP (SAS Institute) software. Models were determined for both unstressed and stressed (t=693 hrs) device performance open-circuit voltage (V_{oc}), current-density (J_{sc}), fill factor (FF), and efficiency (Eff). P-value statistics for testing the significance of regression coefficients for each regressor variable were performed.

Implications of processing on initial performance and stability resulting from these models are discussed in detail elsewhere.^{1,2} An interesting observation during this study concerned the effect of CdS layer thickness. Though the highest initial performance resulted from using the thinnest CdS layers, increased shunting during stress testing negatively impacted stability. This shunting mechanism occurred in conjunction with the more gradual decrease in V_{oc} and FF associated with increased recombination with stress seen in all devices. The use of oxygen during the VCC process had a dramatic effect on reducing the more catastrophic shunt-related mechanism. Figure 1 shows the % change in Eff measured for thick CdTe (11 microns) devices using the thinnest (60 nm) CdS layers, with (solid circles) and without (open circles) NP etch, and with (solid lines) and without (dashed lines) oxygen (100 torr) during the VCC process.

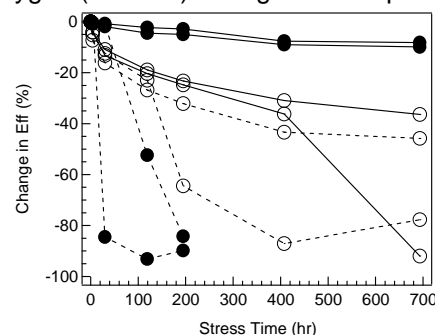


Fig. 1 Efficiency Degradation vs. Stress Time

In addition to the obvious benefit of oxygen, this figure also shows the subtle interaction between NP etch and oxygen where NP etched films require the

use of oxygen during the VCC process in order to be effective. Glancing angle x-ray diffraction (GIXRD) of device-representative CdTe film surfaces reveal the presence of various Te-oxide, and possibly cadmium tellurate and oxychloride phases resulting from the treatment of as-grown CdTe films in VCC processes containing oxygen. Though surface oxides are completely removed by NP etch, the presence of oxides along grain boundaries perpendicular to the film surface is suspected. A review of published thermodynamic data² concerning the reaction of CdTe with Cu, Cl and O suggests that oxidation of Cu dopant (the diffusion of which is known to be problematic), either by reduction of TeO₂ or other oxide phases present at grain boundaries is possible and may help reduce Cu diffusion in much the same way that Cu is "gettered" by Te in NP-etched devices³.

3.2 The Effect of Graphite Layers

The stability of CdTe devices made using four different back contact structures was studied⁴. These structures used either Ag or Ni-based organic pastes as the primary metallic conductor. In half of these devices, the Cu-doped graphite layer was left intact between the metal and the NP-etched CdTe surface during processing (graphite/Ag and graphite/Ni). In the remaining devices, the graphite layer was removed after the 280°C dopant drive step (Ag-only and Ni-only).

No measurable difference in performance or stability was observed among devices with the graphite layer present. The graphite in this case appears to behave like a diffusion barrier, possibly due to a cation exchange mechanism involving the polyacrylic acid (PAA) constituent of this paste. In the absence of graphite, devices showed much faster degradation.

Capacitance-voltage (CV) measurements were used to determine hole carrier concentration as a function of depletion width in unstressed and stressed (712 hrs) devices (Fig. 2).

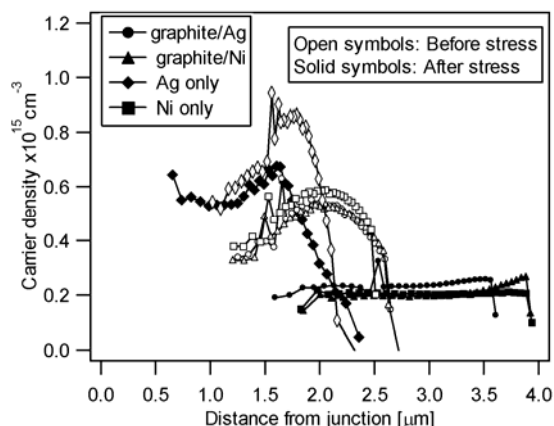


Fig. 2 CV profiles vs. Back Contact Structure

CV profiles before and after stress appear to behave identically with the sole exception of the Ag-only case.

The decreased carrier density and increased depletion width after stress observed in the graphite/Ni, graphite/Ag, and Ni-only devices is commonly observed in cells where Cu is depleted from the back contact⁵. The absence of this behavior in the Ag-only devices may be due to replenishment of Ag from the contact itself. Ag is known to be a rapid diffuser, as well as dopant in CdTe.

The rapid diffusion of Ag in CdTe, particularly at grain boundaries resulted in greater micro non-uniformity formation with stress for the Ag-only devices relative to other cells as determined by light beam induced current (LBIC) measurements. For Ni-only devices, Ni diffusion was minimized by the formation of a Ni₃Te₂ layer detected by GIXRD at the Ni-CdTe interface. Shunting was not observed in the Ni-only case (as it was for the Ag-only devices). However, the increased resistance of this layer contributed to increased series resistance.

4. Conclusions

Cu oxidation, graphite layer diffusion barriers, and intermetallic phase formation were used to explain improved stability observed within the context of two studies involving CdS/CdTe devices. Future work will focus on maintaining stability while reducing the thickness of CSS grown CdTe devices.

ACKNOWLEDGEMENTS

This work was performed under DOE contract DE-AC36-99-GO10337. We also acknowledge useful discussions with Jim Sites of Colorado State University and Sally Asher of NREL.

REFERENCES

- ¹D. Albin, T. McMahon, T.J. Berniard, J. Pankow, S. Demtsu, and R. Noufi, *Proc. 31st IEEE PVSC* (2005), in press.
- ²D.S. Albin, S.H. Demtsu, and T.J. McMahon, *Thin Solid Films* (2005), in review.
- ³D. Albin, R. Dhere, X. Wu, T. Gessert, M.J. Romero, Y. Yan, and S. Asher, *MRS Proc. Vol. 719 Defect and Impurity Engineered Semiconductors and Devices III* 383-388 (2002).
- ⁴S.H. Demtsu, D.S. Albin, J.W. Pankow, and A. Davies, *Sol. Energy Matls & Sol. Cells* (2005), in review.
- ⁵C.R. Corwine, A.O. Pudov, M. Gloeckler, S.H. Demtsu, and J.R. Sites, *Sol. Energy Matls & Sol. Cells*, 82, 481-489 (2004).

MAJOR FY 2005 PUBLICATIONS

(in addition to those listed above)

- T.J. McMahon, T.J. Berniard, and D.S. Albin, *J. of Appl. Phys.* 97 054503 (2005).
 T.J. McMahon, T.J. Berniard, D.S. Albin, and S.H. Demtsu, *Proc. 31st IEEE PVSC* (2005).
 F.H. Seymour, V. Kaydanov, T.R. Ohno, and D. Albin, *Appl. Phys. Lett.*, (2005), accepted for publication.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.

1. REPORT DATE (DD-MM-YYYY) November 2005		2. REPORT TYPE Conference Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Polycrystalline Thin Film Device Degradation Studies			5a. CONTRACT NUMBER DE-AC36-99-GO10337		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S) D.S. Albin, S.H. Demtsu, T.J. McMahon, A. Davies, J.W. Pankow, and R. Noufi			5d. PROJECT NUMBER NREL/CP-520-39003		
			5e. TASK NUMBER PVA6.4301		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				8. PERFORMING ORGANIZATION REPORT NUMBER NREL/CP-520-39003	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S) NREL	
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER	
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT (Maximum 200 Words) Oxygen during vapor CdCl ₂ (VCC) treatments significantly reduced resistive shunts observed in CdS/CdTe polycrystalline devices using thinner CdS layers during 100 °C, open-circuit, 1-sun accelerated stress testing. Cu oxidation resulting from the reduction of various trace oxides present in as-grown and VCC treated films is the proposed mechanism by which Cu diffusion, and subsequent shunts are controlled. Graphite paste layers between metallization and CdTe behave like diffusion barriers and similarly benefit device stability. Ni-based contacts form a protective Ni ₂ Te ₃ intermetallic layer that reduces metal diffusion but degrades performance through increased series resistance.					
15. SUBJECT TERMS Photovoltaics; solar; polycrystalline; thin film; PV; NREL					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)